



TEST REPORT

According to ANSI/IES LM-80-15

For

Hongli Zhihui Group Co.,Ltd. Guangzhou Branch

Room 316, Building 2, No.1, Xianke Yi Road, Huadong Town, Huadu District, Guangzhou, China

Model: HL-C3535K9W1EA(Ra1)-FC

Report Type: 6000 Hours Test Report		Product Type: LED Package	
Reviewed By:	Pote Wang	<i>Pote Wang</i>	
Report Number:	RSZ201026503-10-1-6000		
Test Date:	2020-11-23 to 2021-08-20		
Report Date:	2021-10-11		
Approved by:	Bill Xiong / EE Engineer		
Prepared By:	Bay Area Compliance Laboratories Corp. (Dongguan). No.12, Pulong East 1 st Road, Tangxia Town, Dongguan, Guangdong, China. Tel: +86-0769-86858888 Fax:+86-0769-86858588		

TABLE OF CONTENTS

1 - General Information	3
1.1 Description of LED Light Sources	3
1.2 Standards and Reference Documentations	4
1.3 Testing Equipment	4
1.4 Drive Level	4
1.5 Ambient Conditions for Maintenance Test	5
1.6 Photometric Measurement Method and Uncertainty.....	5
1.7 Statement of Traceability	5
1.8 Sample Set.....	5
2 - Summary of Test Result	6
3 - Test Data	7
3.1 Data Set 1, 55°C, 800mA (400-700nm Photon Flux Maintenance)	7
3.2 Data Set 1, 55°C, 800mA (Forward Voltage).....	8
3.3 Data Set 1, 55°C, 800mA (Wavelength)	9
3.4 Data Set 2, 105°C, 800mA (400-700nm Photon Flux Maintenance)	10
3.5 Data Set 2, 105°C, 800mA (Forward Voltage).....	11
3.6 Data Set 2, 105°C, 800mA (Wavelength)	12
4 - DUT Photo	13
4.1 Mechanical Dimensions	13
4.2 DUT Photo.....	13
Directions	14

1 - General Information

1.1 Description of LED Light Sources

Sample Size:

60 PCS test samples were in good condition and received on 2020-10-26. The samples were numbered from 1 to 30 and 31 to 60.

Manufacturer:	Hongli Zhihui Group Co.,Ltd. Guangzhou Branch
Part Number:	HL-C3535K9W1EA(Ra1)-FC
Part Type:	LED Package
#Drive Level:	DC 800mA
#Wavelength:	601nm
#Power:	2.34 W
#Average Current Density per LED die:	410mA/mm ²
#Average Power Density per LED die:	1.2W/mm ²
#CRI:	70
#Die Spacing:	NA

Sampling Method:

LED samples for IESNA LM-80 testing consist of units built from a minimum of three manufacturing lots with each manufacturing lot built from different wafer lots built on non-consecutive days.

These manufacturing lots are picked to represent a wide parametric distribution.

Family products covered by this report:

According to *ENERGY STAR[®] Requirements for the Use of LM-80 Data*, the following products can be covered by this report base on the information and declaration provided by manufacturer. The information of these models shows that the covered products meet all section 4 requirements of *ENERGY STAR[®] Requirements for the Use of LM-80 Data* (September 28, 2017)

This report covers the following models:

Model Name	Total Input Current (mA)	Power (W)	CCT (K)	Number of dies	Driver current per die(mA)	Current Density per Die (mA/mm ²)	Power Density per PCB (W/mm ²)	Die Spacing (mm)
HL-C3535K9W1EA(Ra1)-FC	800	2.34	2700	1	800	410	0.1932	/
HL-C3535K9W1EA(Ra1)-FC	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535K9W1EA(Ra1)-FC-LVR	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W1EA(Ra1)-FC	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535F77W1EA(Ra1)-FC-LVR	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W1GA(Ra1)-FC	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535K9W1GA(Ra1)-FC-LVR	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W1GA(Ra1)-FC	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535F77W1GA(Ra1)-FC-LVR	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W1EA(Ra1)-FC(Ag60)	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W1EA(Ra1)-FC(Ag60)	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W1EA(Ra1)-FC(Au120)-CY	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W1EA(Ra1)-FC(Au120)-CY	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W1GA(Ra1)-FC(Au120)-CY	800	2.34	2700-6500	1	800	410	0.1932	/

Model Name	Total Input Current (mA)	Power (W)	CCT (K)	Number of dies	Driver current per die(mA)	Current Density per Die (mA/mm ²)	Power Density per PCB (W/mm ²)	Die Spacing (mm)
HL-C3535F77W1GA(Ra1)-FC(Au120)-CY	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W3GA(Ra1)-FC	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W3GA(Ra1)-FC	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W5GA(Ra1)-FC	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W5GA(Ra1)-FC	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W3GA(Ra1)-FC-LVR	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W3GA(Ra1)-FC-LVR	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W5GA(Ra1)-FC-LVR	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W5GA(Ra1)-FC-LVR	500	1.4	2700-6500	1	500	383	0.1176	/
HL-C3535K9W1GA(Ra1)-FC-LVR-QX	800	2.34	2700-6500	1	800	410	0.1932	/
HL-C3535F77W5GA(Ra1)-FC-LVR-QX	500	1.4	2700-6500	1	500	383	0.1176	/

1.2 Standards and Reference Documentations

- ANSI/IES LM-80-15: IES Approved Method for Measuring Lumen Maintenance of LED Light Sources.
- CIE 127:2007: Measurement of LEDs
- ANSI/ASABE S640 JUL2017 Quantities and Units of Electromagnetic Radiation for Plants (Photosynthetic Organisms) (This standard was not accredited by IAS)
- ANSI/ASABE S642 SEP2018: Recommended Methods for Measurement and Testing of LED Products for Plant Growth and Development (This standard was not accredited by IAS)

1.3 Testing Equipment

Device	Manufacture	Model No	Serial No	Calibration date	Calibration due date
High Accuracy Array Spectroradiometer	EVERFINE	HAAS 2000	P600674CM5391140	2020-10-22	2021-10-21
0.5M Integrating Sphere	EVERFINE	0.5m	NA	2020-10-22	2021-10-21
LED Test Source	EVERFINE	LTS-300	P185616CJ1391143	2020-10-21	2021-10-20
Standard Light Source	EVERFINE	D062	1011093	2020-10-20	2021-10-19
High Accuracy Array Spectroradiometer	EVERFINE	HAAS 2000	P600674CM5391140	2020-10-22	2021-10-21
Multilayer aging machine	BACL	B2-270	20022	2021-02-24	2022-02-23
Digital CC&CV DC Power Supply	EVERFINE	WY5015	11090009	2021-02-24	2022-02-23

1.4 Drive Level

Samples are driven with a constant direct current (DC) during maintenance test, photometric and electrical measurement. The current value was regulated to within $\pm 3\%$ of the specified value of the manufacturer during maintenance test, and was within $\pm 0.5\%$ during photometric and electrical measurement test.

1.5 Ambient Conditions for Maintenance Test

For lumen maintenance test, samples within one data set, were installed on cooling boards in thermal chambers with minimal ambient airflow. The case temperature and ambient temperature was monitored by thermocouples which one was soldered to the coldest DUTs' case (TMP_{LED}) location, while the other is mounted at a distance of 5 mm above the TMP location.

During life testing, TMP_{LED} of the coldest LEDs were maintained at a temperature that was greater than or equal to 2°C below the corresponding nominal case temperature. Surrounding air was maintained at a temperature that was greater than or equal to 5°C below the corresponding nominal case temperature. Thermocouples were shielded from direct DUT optical radiation and comply with ASTM E230 Table 1 "Special Limits".

Samples were connected to DC power supply in series circuits with a constant current. The forward current was regulated to within ±3% of the specified value of the manufacturer.

The relative humidity within chamber was kept less than 65% during test.

For photometry measurement, the ambient temperature during test was set to 25°C ± 2°C, RH <65%.

1.6 Photometric Measurement Method and Uncertainty

Integrating sphere and spectroradiometer is used to measure spectral power distribution and photon flux. 2π measurement was used and sample was driven by DC power supply. The forward current was regulated to within ±0.5% of the nominal value. The test system was calibrated by halogen reference lamp. The ambient temperature during test was set to 25°C ± 2°C, RH <65%. The temperature measurement point was located in the sphere and the temperature was detected by a temperature probe.

1.7 Statement of Traceability

Bay Area Compliance Laboratories Corp. (Dongguan) attested that all calibration has been performed using suitable standards traceable to National Primary Standards and International System of Units (SI).

1.8 Sample Set

Data Set 1: 55°C, 800mA

Part Number: HL-C3535K9W1EA(Ra1)-FC
Number of Units: 30
Case Temperature: >53°C
Ambient Temperature: >50°C
Life Test Drive Current: 800mA
Measurement Current: 800mA

Data Set 2: 105°C, 800mA


Part Number: HL-C3535K9W1EA(Ra1)-FC
Number of Units: 30
Case Temperature: >103°C
Ambient Temperature: >100°C
Life Test Drive Current: 800mA
Measurement Current: 800mA

2 - Summary of Test Result

Data Set:	Sample Size	Failures Observed:	Test Interval	Test Duration	α	β	Reported TM-21 Q ₇₀ Lifetime	Reported TM-21 Q ₉₀ Lifetime
1	30	0	1000hrs	6000hrs	2.272E-06	1.003	>36000 hours	>36000 hours
2	30	0	1000hrs	6000hrs	2.728E-06	1.002	>36000 hours	>36000 hours

Average Photon Flux Maintenance, Photosynthetic 400-700nm (PFM_p) (Percentage of Initial)

Data Set:	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	100.09%	99.76%	99.62%	99.46%	99.16%	98.90%
2	99.90%	99.55%	99.39%	99.13%	98.78%	98.52%

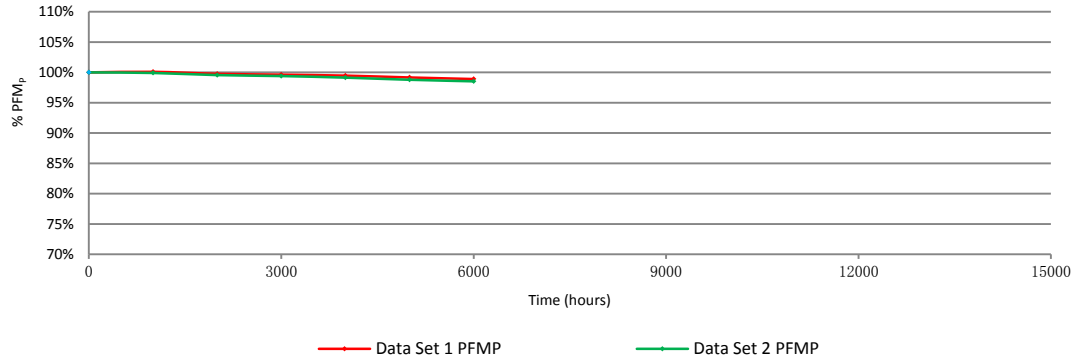

3 - Test Data

3.1 Data Set 1, 55°C, 800mA (400-700nm Photon Flux Maintenance)

No.	Φ_p ($\mu\text{mol} \times \text{s}^{-1}$)	400-700nm Photon Flux Maintenance (%)					
		0hr(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs
1	4.7180	100.11%	99.75%	99.70%	99.43%	99.19%	99.15%
2	4.6150	100.09%	99.93%	99.85%	99.70%	99.37%	99.00%
3	4.6410	100.02%	99.76%	99.61%	99.55%	99.01%	98.90%
4	4.6790	100.02%	99.74%	99.64%	99.40%	99.17%	98.91%
5	4.6410	100.22%	99.91%	99.72%	99.42%	99.22%	99.07%
6	4.6360	100.19%	99.94%	99.76%	99.68%	99.25%	99.09%
7	4.6450	100.43%	100.15%	99.85%	99.72%	99.55%	99.29%
8	4.6580	100.15%	99.76%	99.61%	99.51%	99.40%	98.86%
9	4.6850	100.23%	99.87%	99.72%	99.49%	99.21%	98.95%
10	4.6180	100.11%	99.83%	99.78%	99.42%	99.16%	98.77%
11	4.6410	100.22%	100.09%	100.04%	99.98%	99.74%	99.25%
12	4.6620	100.15%	99.96%	99.91%	99.74%	99.51%	99.29%
13	4.6550	100.02%	99.89%	99.83%	99.72%	99.36%	99.12%
14	4.5430	100.15%	99.67%	99.65%	99.52%	99.14%	99.01%
15	4.5100	100.20%	100.02%	99.87%	99.65%	99.42%	99.29%
16	4.5810	100.13%	99.76%	99.67%	99.39%	99.13%	98.95%
17	4.6750	100.06%	99.61%	99.49%	99.34%	98.97%	98.84%
18	4.6490	100.11%	99.66%	99.59%	99.46%	99.14%	98.80%
19	4.7350	99.98%	99.75%	99.37%	99.28%	99.05%	98.75%
20	4.6300	99.85%	99.65%	99.44%	99.24%	98.92%	98.70%
21	4.6750	100.19%	99.70%	99.64%	99.53%	99.38%	98.84%
22	4.6930	100.02%	99.55%	99.51%	99.34%	98.93%	98.74%
23	4.6650	100.09%	99.66%	99.36%	99.34%	98.93%	98.84%
24	4.6530	100.02%	99.57%	99.29%	99.10%	98.67%	98.60%
25	4.6870	99.85%	99.47%	99.32%	99.04%	98.63%	98.40%
26	4.6580	100.15%	99.96%	99.42%	99.40%	99.16%	98.82%
27	4.6750	100.11%	99.66%	99.57%	99.51%	99.27%	98.87%
28	4.6840	100.06%	99.53%	99.49%	99.40%	98.98%	98.70%
29	4.6730	100.02%	99.57%	99.53%	99.51%	99.25%	98.78%
30	4.6280	99.87%	99.35%	99.22%	98.98%	98.70%	98.53%
Avg.	4.6503	100.09%	99.76%	99.62%	99.46%	99.16%	98.90%
Med.	4.6565	100.11%	99.75%	99.62%	99.44%	99.16%	98.86%
st dev	0.0457	0.12%	0.19%	0.20%	0.21%	0.26%	0.22%
Min.	4.5100	99.85%	99.35%	99.22%	98.98%	98.63%	98.40%
Max.	4.7350	100.43%	100.15%	100.04%	99.98%	99.74%	99.29%

3.2 Data Set 1, 55°C, 800mA (Forward Voltage)

No.	Forward Voltage (V)						
	0hr(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	2.910	2.927	2.928	2.921	2.911	2.924	2.928
2	2.920	2.939	2.939	2.936	2.958	2.961	2.957
3	2.907	2.923	2.922	2.921	2.917	2.929	2.932
4	2.908	2.923	2.923	2.917	2.916	2.947	2.930
5	2.925	2.931	2.932	2.934	2.935	2.948	2.937
6	2.922	2.935	2.940	2.931	2.943	2.922	2.921
7	2.924	2.939	2.938	2.944	2.930	2.931	2.940
8	2.925	2.936	2.935	2.927	2.935	2.952	2.936
9	2.919	2.939	2.936	2.942	2.947	2.937	2.936
10	2.920	2.936	2.933	2.934	2.934	2.952	2.958
11	2.926	2.941	2.939	2.935	2.943	2.945	2.941
12	2.917	2.933	2.934	2.931	2.931	2.957	2.952
13	2.903	2.925	2.923	2.928	2.927	2.926	2.926
14	2.916	2.932	2.933	2.925	2.934	2.947	2.952
15	2.906	2.920	2.919	2.913	2.927	2.908	2.926
16	2.914	2.931	2.928	2.923	2.933	2.937	2.939
17	2.919	2.934	2.933	2.923	2.947	2.948	2.937
18	2.915	2.930	2.930	2.920	2.926	2.917	2.927
19	2.929	2.945	2.943	2.934	2.936	2.941	2.945
20	2.904	2.916	2.915	2.908	2.917	2.921	2.930
21	2.926	2.941	2.939	2.928	2.928	2.924	2.928
22	2.919	2.933	2.932	2.922	2.916	2.931	2.928
23	2.919	2.933	2.933	2.925	2.920	2.943	2.931
24	2.929	2.946	2.944	2.946	2.936	2.926	2.926
25	2.929	2.947	2.944	2.947	2.939	2.946	2.941
26	2.919	2.932	2.931	2.927	2.919	2.915	2.921
27	2.917	2.933	2.934	2.923	2.919	2.937	2.920
28	2.917	2.934	2.934	2.923	2.919	2.929	2.909
29	2.902	2.918	2.915	2.906	2.916	2.925	2.929
30	2.906	2.921	2.922	2.913	2.917	2.926	2.924
Avg.	2.917	2.932	2.932	2.927	2.929	2.935	2.934
Med.	2.919	2.933	2.933	2.926	2.929	2.934	2.931
st dev	0.008	0.008	0.008	0.010	0.012	0.013	0.011
Min.	2.902	2.916	2.915	2.906	2.911	2.908	2.909
Max.	2.929	2.947	2.944	2.947	2.958	2.961	2.958

3.3 Data Set 1, 55°C, 800mA (Wavelength)

No.	Wavelength (nm)						
	0hr(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	602.0	602.0	602.0	603.6	603.2	601.3	602.1
2	602.0	602.0	602.0	602.3	602.9	602.0	603.7
3	602.0	602.0	602.0	604.8	601.7	603.8	604.0
4	602.0	602.0	602.0	600.2	601.7	604.8	604.5
5	602.0	602.0	601.8	602.5	603.5	602.6	603.7
6	601.8	601.7	602.0	601.5	602.5	602.5	604.0
7	601.3	601.9	601.3	602.7	603.7	604.0	602.0
8	602.0	602.0	602.0	600.2	602.1	603.5	603.0
9	602.0	602.1	601.8	602.9	603.6	602.1	603.7
10	601.7	602.0	602.0	601.2	600.5	604.8	603.3
11	602.0	602.0	602.0	603.2	603.7	603.3	602.0
12	602.0	602.0	602.0	603.5	604.0	600.5	602.1
13	602.0	602.0	601.3	604.0	602.9	602.3	602.5
14	602.0	601.7	602.0	601.5	604.0	601.3	602.4
15	602.0	601.7	602.0	603.5	602.4	603.3	603.0
16	602.0	602.2	601.7	602.9	602.5	602.4	603.7
17	601.3	602.0	602.0	602.5	603.8	601.3	602.9
18	601.7	602.0	602.0	603.3	601.3	602.9	604.8
19	602.0	602.0	602.3	602.5	603.2	602.5	603.5
20	601.7	602.1	602.0	601.0	601.2	601.3	599.8
21	602.1	602.0	602.0	603.3	602.1	600.9	603.2
22	602.0	602.0	602.0	601.7	601.7	602.3	602.5
23	602.0	601.7	602.0	603.5	604.4	602.4	603.7
24	602.0	602.0	602.0	602.3	602.7	601.3	605.2
25	602.0	602.0	605.0	602.1	603.2	603.2	603.7
26	602.0	602.0	602.0	602.5	602.9	602.9	602.3
27	602.1	602.1	602.0	601.5	603.3	603.8	604.8
28	601.6	601.3	601.9	602.9	601.0	604.5	603.0
29	602.0	602.0	601.6	601.3	603.2	602.1	605.0
30	602.0	602.0	601.3	604.4	603.7	602.9	603.6
Avg.	601.9	602.0	602.0	602.5	602.8	602.6	603.3
Med.	602.0	602.0	602.0	602.5	602.9	602.5	603.4
st dev	0.2	0.2	0.6	1.1	1.0	1.1	1.1
Min.	601.3	601.3	601.3	600.2	600.5	600.5	599.8
Max.	602.1	602.2	605.0	604.8	604.4	604.8	605.2

3.4 Data Set 2, 105°C, 800mA (400-700nm Photon Flux Maintenance)

No.	Φ_p ($\mu\text{mol} \times \text{s}^{-1}$)	400-700nm Photon Flux Maintenance (%)					
		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
31	4.6640	99.89%	99.53%	99.40%	99.08%	98.65%	98.41%
32	4.6530	100.02%	99.70%	99.55%	99.25%	98.90%	98.73%
33	4.6520	99.85%	99.51%	99.38%	99.08%	98.69%	98.39%
34	4.6380	100.02%	99.57%	99.44%	99.18%	98.77%	98.49%
35	4.6570	99.91%	99.53%	99.42%	99.29%	98.95%	98.60%
36	4.6140	99.93%	99.57%	99.37%	99.13%	98.81%	98.61%
37	4.6440	99.83%	99.72%	99.66%	99.42%	99.07%	98.84%
38	4.6730	99.91%	99.61%	99.51%	99.38%	99.04%	98.84%
39	4.6550	99.94%	99.53%	99.46%	99.25%	98.84%	98.67%
40	4.6490	99.78%	99.44%	99.18%	98.97%	98.54%	98.37%
41	4.6300	99.91%	99.89%	99.11%	98.88%	98.42%	98.12%
42	4.6370	99.91%	99.31%	99.20%	98.99%	98.60%	98.43%
43	4.6540	99.85%	99.53%	99.33%	99.18%	98.93%	98.73%
44	4.7150	99.72%	99.51%	99.34%	99.17%	98.83%	98.56%
45	4.6920	99.87%	99.51%	99.42%	99.10%	98.74%	98.57%
46	4.6350	99.96%	99.57%	99.48%	99.33%	99.03%	98.66%
47	4.6590	99.98%	99.66%	99.53%	99.27%	98.95%	98.67%
48	4.6780	100.09%	99.64%	99.51%	99.29%	99.04%	98.61%
49	4.6900	100.06%	99.74%	99.42%	99.08%	98.70%	98.36%
50	4.6910	99.81%	99.53%	99.04%	98.76%	98.47%	98.12%
51	4.6700	99.98%	99.66%	99.57%	99.21%	98.89%	98.61%
52	4.6370	99.87%	99.57%	99.50%	99.20%	99.09%	98.45%
53	4.6320	100.06%	99.55%	99.50%	99.14%	98.73%	98.47%
54	4.5890	99.89%	99.48%	99.41%	99.15%	98.78%	98.58%
55	4.6580	99.85%	99.53%	99.42%	99.18%	98.73%	98.43%
56	4.6090	99.83%	99.52%	99.37%	99.13%	98.87%	98.65%
57	4.6360	99.81%	99.53%	99.40%	99.03%	98.60%	98.32%
58	4.7060	99.79%	99.51%	99.43%	99.15%	98.85%	98.60%
59	4.6760	99.72%	99.40%	99.19%	98.91%	98.52%	98.25%
60	4.6770	99.87%	99.27%	99.06%	98.85%	98.44%	98.38%
Avg.	4.6557	99.90%	99.55%	99.39%	99.13%	98.78%	98.52%
Med.	4.6545	99.89%	99.53%	99.42%	99.15%	98.79%	98.56%
st dev	0.0284	0.10%	0.12%	0.15%	0.16%	0.19%	0.18%
Min.	4.5890	99.72%	99.27%	99.04%	98.76%	98.42%	98.12%
Max.	4.7150	100.09%	99.89%	99.66%	99.42%	99.09%	98.84%

3.5 Data Set 2, 105°C, 800mA (Forward Voltage)


No.	Forward Voltage (V)						
	0hr(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
31	2.926	2.942	2.940	2.931	2.938	2.933	2.947
32	2.922	2.935	2.933	2.925	2.936	2.930	2.944
33	2.914	2.930	2.928	2.921	2.932	2.930	2.930
34	2.929	2.942	2.941	2.931	2.947	2.924	2.945
35	2.925	2.944	2.943	2.930	2.943	2.941	2.942
36	2.922	2.936	2.935	2.923	2.935	2.933	2.926
37	2.903	2.920	2.919	2.910	2.921	2.937	2.930
38	2.913	2.928	2.928	2.922	2.921	2.912	2.923
39	2.928	2.922	2.921	2.915	2.924	2.934	2.925
40	2.919	2.933	2.934	2.932	2.944	2.944	2.925
41	2.917	2.932	2.932	2.925	2.943	2.934	2.947
42	2.924	2.936	2.935	2.928	2.925	2.935	2.938
43	2.915	2.932	2.933	2.927	2.920	2.933	2.934
44	2.928	2.947	2.949	2.935	2.939	2.925	2.940
45	2.929	2.946	2.943	2.936	2.928	2.943	2.958
46	2.903	2.934	2.916	2.912	2.916	2.917	2.926
47	2.922	2.940	2.939	2.929	2.928	2.948	2.954
48	2.924	2.942	2.940	2.935	2.937	2.957	2.956
49	2.924	2.942	2.943	2.935	2.949	2.946	2.952
50	2.914	2.932	2.931	2.924	2.929	2.959	2.946
51	2.913	2.932	2.930	2.922	2.912	2.925	2.946
52	2.915	2.933	2.932	2.925	2.918	2.940	2.932
53	2.909	2.920	2.919	2.912	2.924	2.927	2.947
54	2.906	2.923	2.926	2.918	2.925	2.920	2.938
55	2.917	2.934	2.935	2.930	2.935	2.943	2.964
56	2.902	2.917	2.916	2.911	2.914	2.923	2.960
57	2.905	2.920	2.919	2.914	2.930	2.930	2.931
58	2.904	2.920	2.919	2.915	2.923	2.935	2.969
59	2.913	2.931	2.928	2.922	2.921	2.934	2.964
60	2.915	2.935	2.933	2.926	2.936	2.960	2.957
Avg.	2.917	2.933	2.931	2.924	2.930	2.935	2.943
Med.	2.916	2.933	2.933	2.925	2.929	2.934	2.945
st dev	0.008	0.008	0.009	0.008	0.010	0.012	0.013
Min.	2.902	2.917	2.916	2.910	2.912	2.912	2.923
Max.	2.929	2.947	2.949	2.936	2.949	2.960	2.969

3.6 Data Set 2, 105° C, 800mA (Wavelength)

No.	Wavelength (nm)						
	0hr(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
31	602.0	601.8	601.3	601.2	603.2	602.5	602.1
32	602.0	602.1	602.1	602.9	604.8	603.3	604.8
33	602.3	602.0	601.7	602.4	602.1	604.4	604.8
34	602.0	602.1	602.0	602.4	603.7	603.5	604.0
35	602.3	602.0	602.1	602.5	601.3	604.8	604.8
36	602.0	602.0	602.0	604.8	602.3	603.7	602.9
37	601.6	602.0	601.5	602.4	602.4	604.4	602.3
38	601.8	602.1	602.0	603.2	602.9	602.5	602.7
39	602.0	602.0	602.0	602.9	603.2	605.4	604.2
40	601.3	602.0	602.0	601.3	602.5	602.5	602.5
41	601.8	602.0	601.7	600.4	603.7	604.6	603.2
42	601.3	602.0	604.6	602.3	602.7	602.6	604.4
43	602.1	602.0	602.0	602.4	603.7	602.7	603.8
44	602.0	604.8	602.3	603.5	602.5	603.6	603.2
45	602.0	601.0	602.0	604.0	603.7	603.2	601.2
46	602.0	601.7	602.0	599.8	602.5	602.9	603.3
47	602.0	601.3	604.4	601.3	602.9	602.5	602.7
48	602.0	602.0	602.0	602.1	601.7	604.0	603.2
49	602.0	602.0	604.8	603.2	605.2	602.4	602.3
50	602.0	602.1	601.7	603.2	603.2	602.8	605.2
51	602.0	602.0	602.0	601.7	603.6	601.7	603.5
52	604.9	602.0	602.0	603.5	602.9	602.3	603.7
53	601.7	602.0	602.0	602.5	604.4	601.3	602.1
54	601.6	601.3	602.0	602.7	602.5	602.9	603.6
55	602.0	602.0	602.0	603.2	602.9	601.7	601.4
56	602.0	602.0	601.7	603.7	602.7	601.4	600.9
57	601.7	602.1	601.7	602.3	602.9	604.8	604.8
58	602.0	602.0	602.0	602.5	603.2	603.2	601.3
59	602.0	602.0	602.1	603.7	602.9	604.4	603.5
60	601.3	602.1	602.0	600.9	603.5	602.9	604.5
Avg.	602.0	602.0	602.2	602.5	603.1	603.2	603.2
Med.	602.0	602.0	602.0	602.5	602.9	602.9	603.3
st dev	0.6	0.6	0.8	1.1	0.8	1.1	1.2
Min.	601.3	601.0	601.3	599.8	601.3	601.3	600.9
Max.	604.9	604.8	604.8	604.8	605.2	605.4	605.2

4 - DUT Photo


4.1 Mechanical Dimensions

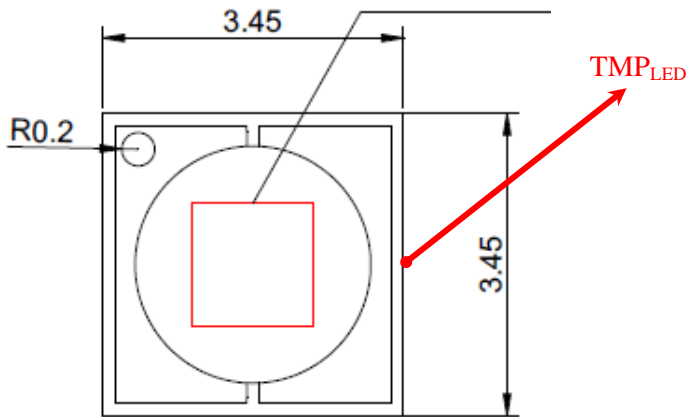

+ -

All dimensions are in millimeter

4.2 DUT Photo

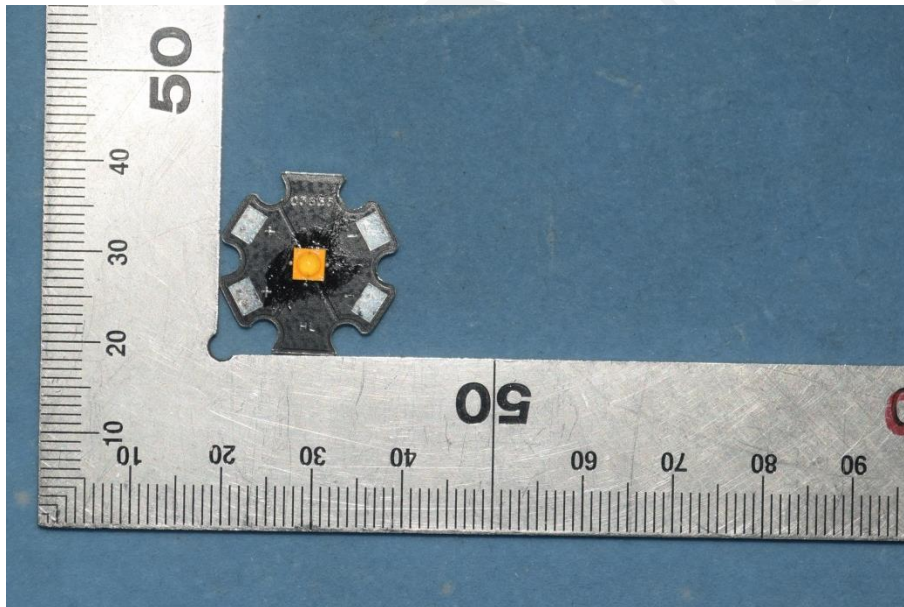

Directions

1. The information marked "superscript #" is provided by the applicant, the laboratory is not responsible for its authenticity and this information can affect the validity of the result in the test report.
2. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.
3. Otherwise required by the applicant or Product Regulations, Decision Rule in this report did not consider the uncertainty.
4. The extended uncertainty given in this report is obtained by combining the standard uncertainty times the coverage factor K with the 95% confidence interval.
5. This report cannot be reproduced except in full, without prior written approval of the Company.
6. This report is valid only with a valid digital signature. The digital signature may be available only under the Adobe software above version 7.0.

*****END OF REPORT*****